



Experimental investigation of cyclic behavior of zeolite cemented sand

M. Saadati, M. Derakhshandi*, A. Bahmanpour, N. Ganjian

Department of Civil Engineering, Science and Research Branch, Islamic Azad University, Tehran, Iran

ABSTRACT: The shear module is of the most crucial soil dynamic properties in seismic geotechnical engineering. The replacement of a part of cement, the production of which is one of the most important sources of CO₂ emission in the world, with natural materials such as zeolite is of great importance. In the present study, the cyclic behaviour of pure sand is compared with the cyclic behaviour of sand grouted with cement and zeolite. The sand used in this research was taken from Babolsar, which is classified as a poorly graded sand based on the Unified soil classification system. The effects of the confining pressure, the shear strain and the replacement of cement by zeolite on the shear modulus are studied. All the specimens were prepared by the wet tamping method and cyclic triaxial tests were performed with three different confining pressures of 100, 200, and 300 kPa in the moderate shear strain range. The results show that Shear modulus values of the cemented sand specimens with a water-to-cement ratio of 1 are greater than that of the pure sand specimens in all ranges of shear strains. The shear modulus values increased with the replacement of cement by zeolite of cemented samples. Therefore, the replacement of cement with zeolite can be considered from an environmental point of view. By increasing the confining pressure, the shear modulus values of the pure sand, cemented sand, zeolite cemented sand specimens increased. This increase is significant for cemented and cemented zeolite specimens at a larger confining pressure range.

Review History:

Received: Aug. 09, 2020

Revised: Jan. 15, 2021

Accepted: Jan. 18, 2021

Available Online: Jan. 29, 2021

Keywords:

Cyclic triaxial test

Babolsar sand

Shear modulus

Cement, Zeolite.

1- Introduction

A method to improve granular soils, which causes important changes in soil properties, including shear strength and deformation module, is cementation. In recent years, much research has been conducted on sand stabilization using cement grouting [1-7] to strengthen soil characteristics.

Li et al. [8] performed resonant column tests on grouted sand specimens, including three different types of grout (a microfine slug-cement suspension with water-to-cement ratio (W/C) of 2, an acrylic solution, and a solution of sodium silicate) and studied the effect of grout type and confining pressure on the dynamic properties of Ottawa sand. The results showed that the microfine slug-cement suspension had greater dynamic module values in the elastic range than the chemical solutions.

Much energy is consumed for cement production, accounting for 7% of global CO₂ emissions [9]. So, the use of pozzolans, especially naturally-occurring pozzolans, as an alternative for cement can be a remarkable option for reducing cement consumption. Since zeolite has appropriate chemical properties and is environmentally-friendly and economical, it has been used in several geotechnical studies.

This research studied the shear module of Babolsar silicate sand improved by zeolite and Portland cement in a moderate range of shear strain using a cyclic triaxial apparatus and analyzed the effect of cement replacement with zeolite, confining pressure, and shear strain on the shear modulus of the specimen.

2- Methodology


The research used Babolsar sand as well as Portland cement type 2 and zeolite of clinoptilolite type. To have samples with uniform density across the height, the wet tamping method was used with reduced density according to the approach proposed by Ladd [10].

3- Results and Discussion


Figure 1 displays the results of the hysteresis loop of the triaxial test of the clean sand, cemented sand, and zeolite-cemented sand sample with a relative density of 50% and effective confining pressure of 200 kPa with isotropic consolidation. The results show that since the specimens were consolidated in the same conditions, the stress-strain graph started from the origin of coordinates.

*Corresponding author's email: m-derakhshandi@srbiau.ac.ir




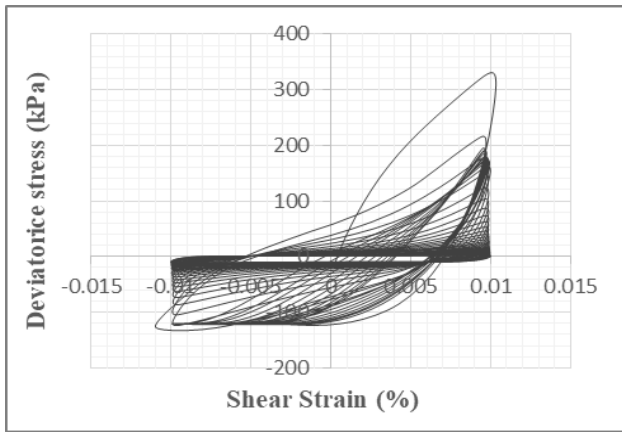

(a)

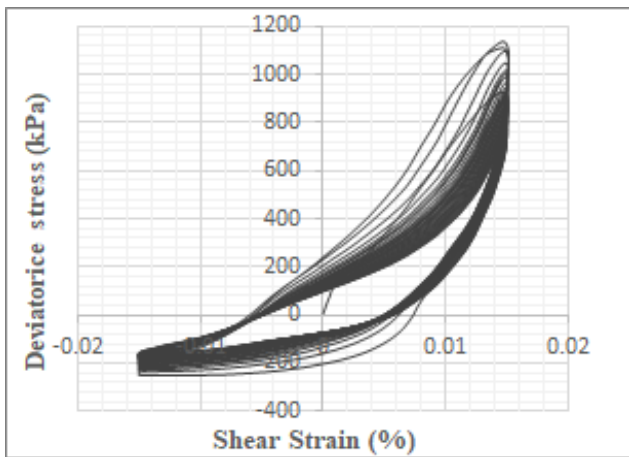

(b)

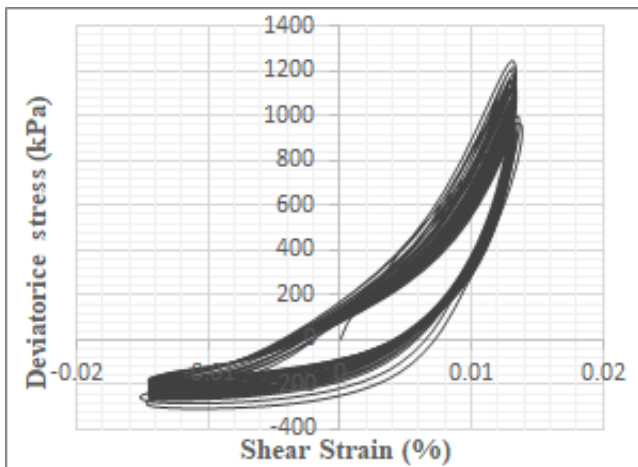

(c)

Fig. 1. Results of the hysteresis loop versus the number of loading cycles a) clean sand, b) cemented sand, c) zeolite-cemented sand sample

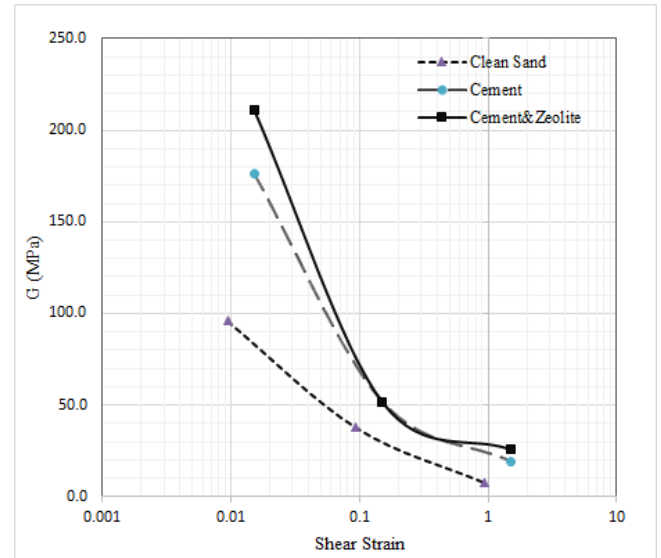


Fig. 2. Variation of the shear modulus with shear strain, confining pressure of 200 kPa

The effect of cementation was studied on the improvement of dynamic properties and the effect of zeolite replacement for cement in cyclic triaxial experiments on clean sand, cemented sand, and zeolite-cemented sand with a water/cement ratio of 1. In all cyclic triaxial experiments, the percentage of cement used in the cemented samples was 4% of the weight ratio of the base soil and the percentage of zeolite used for the zeolite-cemented sample was 30% of the weight ratio of the cement. As is evident in Figure 2, when zeolite was replaced for 30% of the cement in the cemented samples, the shear modulus values were increased. This increase is more evident in the smaller shear strain (0.015%). This behavior is similar to the one reported by Kordnaeij et al. [11] in their bender element experiment on the maximum shear module of a zeolite-cemented sand sample, although they reported a higher coefficient of the shear module ratio of zeolite-cemented sand to clean sand, which is related to the quantity of cement, which was over 20% of the weight ratio of the base sand whereas this ratio was 4% in the present work.

In general, the amounts of SiO_2 and Al_2O_3 versus CaO in the cement pozzolan reaction and hydration have a significant impact on the resistance of the cemented sample. When CaO is adequate, an increase in SiO_2 and Al_2O_3 contents results in a more active pozzolan reaction and higher hardness of the cemented sand sample. When 30% zeolite is replaced for the cement, this means an increase in SiO_2 and Al_2O_3 contents, whereas CaO content is decreased. So, in soil improvement projects, a fraction of cement is replaced with a natural pozzolan, such as zeolite, which is readily extractable and environmentally-friendly and causes a significant increase in soil hardness is of great importance.

4- Conclusions

For all samples, including clean sand, cemented sand, and zeolite-cemented sand samples, an increase in shear strain reduced the shear modulus values.

The shear modulus of the cemented sand samples with a water-to-cement ratio of 1 was greater than that of the clean sand sample across the whole shear strain range.

When confining pressure was increased, the shear modulus of the clean sand, cemented sand, and zeolite-cemented sand samples were increased. This increase was significant for the cemented and zeolite-cemented samples at confining pressure ranges of 200 and 300 kPa.

References

- [1] M. Mollamahmutoglu, Y. Yilmaz, Engineering properties of medium-to-fine sands injected with microfine cement grout, *Marine Georesources & Geotechnology*, 29(2) (2011) 95–109.
- [2] I.N. Markou, A.I. Droudakis, Factors affecting engineering properties of microfine cement grouted sands, *Geotechnical and Geological Engineering*, 31(4) (2013) 1041–1058.
- [3] M. Yildiz, A.S. Soganci, Improvement of the strength of soils which comprises granular pumice by injection of cement under low pressure, *Scientia Iranica Transactions A: Civil Engineering*, 22(1) (2015)81–89.
- [4] P.L. Lovelady, M. Picornell, ‘Sample coupling in resonant column testing of cemented soils’, In: Wolfenden A (ed.) *Dynamic elastic modulus measurements in materials*, ASTM, (1990) pages 180-94.
- [5] A.L. Fernandez, J.C. Santamarina, Effect of cementation on the small-strain parameters of sands, *Canadian Geotechnical Journal*, 38 (2001) 191–9.
- [6] I.A. Pantazopoulos, D.K. Atmatzidis, Dynamic properties of microfine cement grouted sands, *Soil Dynamics and Earthquake Engineering*, 42 (2012) 17–31.
- [7] E. Delfosse-Ribay, I. Djeran-Maigre, R. Cabrillac, D. Gouvenot, Shear modulus and damping ratio of grouted sand, *Soil Dynamics and Earthquake Engineering*, 24 (2004) 461–71.
- [8] N. Li, R.D. Woods, Dynamic behavior of grouted sand, In: Cakmak, AS, (ed.) *Soil structure interaction*, Amsterdam, Elsevier, (1987) pages 221-41.
- [9] P.K. Mehta, Concrete technology for sustainable development *Concrete Technology for a Sustainable development in the 21st Century*, CRC Press, Boca Raton, (1999) p 83.
- [10] R.S. Ladd, (1978) Preparing test specimens using undercompaction, *Geotechnical Testing Journal*, 1(1) (1978) 16-23.
- [11] A. Kordnaeij, R. Ziaie Moayed, M. Soleimani, Small strain shear modulus of sands grouted with zeolite-cement suspension, *Amirkabir Journal of Civil Engineering*, Online publishing, (1397) (In Persian).

HOW TO CITE THIS ARTICLE

M. Saadati, M. Derakhshandi, A. Bahmanpour, N. Ganjian, *Experimental investigation of cyclic behavior of zeolite cemented sand*, *Amirkabir J. Civil Eng.*, 53(12) (2022) 1159-1162.

DOI: 10.22060/ceej.2021.18843.6978



