

A Study on Mechanical Properties, Water Absorption and Microstructure of Cementitious Mortar containing Recycled Admixtures

Ghasem Pachideh¹, Majid Gholhaki^{2*}

1- Ph.D. Candidate, Department of Civil Engineering, Semnan University, Semnan, Iran.

ghpachideh@semnan.ac.ir

2- Associate Professor, Department of Civil Engineering, Semnan University, Semnan, Iran.

mgholhaki@semnan.ac.ir.

ABSTRACT

Economic concerns and environmental issues have led to increased use of recycled materials in cementitious mortars. In fact, to mitigate the adverse effects of cement, it can be partially replaced with recycled materials. In this paper, cement was partially replaced with iron, rubber, glass and eggshell powders (IP, RP, GP and EP) by 7, 14, 21 and 28% and then, compressive and tensile strength, water absorption and microstructure of the specimens were assessed. The strength tests, as well as microstructure analysis, were conducted at the age of 28-day and the water absorption was tested at the ages of 7, 28, 56 and 90 days. Based on the results, use of all powders by 14%, enhances the compressive strength up to 14%. Moreover, it was found that up to replacement ratio of 28%, the tensile strength is greater than that of the control specimen although, in the case of 7% admixtures, maximum tensile strength is achieved. In addition, water absorption of the specimens containing GP and EP up to 35% replacement ratio, is less than that of the other specimens, which was well observed in the SEM analyses.

KEYWORDS

Cement mortar, Waste pozzolan, mechanical properties, Water Absorption, SEM.

1. Introduction

In recent decades, most countries are seeking strategies to efficiently recycle waste materials [1-5]. Based on the review of the latest studies, the wastes could be used for industrial requirements through which the technical, economic and environmental demands are fulfilled. Today, the rapid development of the industry has accentuated the need for energy production and in turn, the environmental challenges have increased subsequently. Accordingly, to avoid depletion of the natural aggregates and adopt an eco-friendly solution, waste materials could be recycled and reused in the construction and building projects [6]. In this respect, waste materials have received significant attention to be partially used as a replacement for aggregates in the concrete, by which the concrete properties could be ameliorated as well [7,8].

2. Methodology

The specimens were prepared in two different forms to conduct the compressive and tensile strength tests. In this respect, standard cube specimens with size of 50×50×50 mm were constructed for testing the compressive strength and the standard dogbone-shaped briquettes containing iron, glass, rubber and eggshell powder (with particle size of 50 to 60 μm) with replacement ratios of 7, 14, 21 and 28%, were prepared to carry out the direct tension tests. In addition, the water absorption test was performed in conformation with the relevant standard at the ages of 7, 28, 56 and 90 days.

Noteworthy, prior to using the waste materials into the concrete mixes, they were kept in the electric furnace with a temperature of 100°C for 24 to 48 hours so that their humidity is completely lost. In the next step, these materials were crushed by special mills and then, ground to powders with the required size of particles.

It is worthwhile that the wastes to be used in the concrete mixes are taken from the places special for depositing such materials outside the city. The wastes employed in our tests include powders of glass, iron, eggshell, and rubber that are recycled from glass pieces, iron filings, eggshells, and car tires. To prepare the powders, first, the materials with large pieces were collected and then, powdered by the electric grinder. For this purpose, the grinder blades were adjusted to produce particles of the size ranging from 50 to 60 μm. As given in Table 1 presents the concrete mix designs in detail, the water-to-cement (W/C) ratio is taken equal to 0.4.

Table 1. Summary of the Mix Designs (kg/m³)

Mix ID	Sand	Cement	Water	Pozzolan (%)				
				0	7	14	21	28
A	1287	770	308	-	-	-	-	-
EP-7%	1287	716	308	-	54	-	-	-
EP-14%	1287	662	308	-	-	108	-	-
EP-21%	1287	608.5	308	-	-	-	161.5	-
EP-28%	1287	554.5	308	-	-	-	-	215.5
GP-7%	1287	716	308	-	54	-	-	-
GP-14%	1287	662	308	-	-	108	-	-
GP-21%	1287	608.5	308	-	-	-	161.5	-
GP-28%	1287	554.5	308	-	-	-	-	215.5
IP-7%	1287	716	308	-	54	-	-	-
IP-14%	1287	662	308	-	-	108	-	-
IP-21%	1287	608.5	308	-	-	-	161.5	-
IP-28%	1287	554.5	308	-	-	-	-	215.5
RP-7%	1287	716	308	-	54	-	-	-
RP-14%	1287	662	308	-	-	108	-	-
RP-21%	1287	608.5	308	-	-	-	161.5	-
RP-28%	1287	554.5	308	-	-	-	-	215.5

3. Results and Discussion

Compressive Strength Test

The trend of variations in the compressive strength versus an increase in the replacement ratio of the pozzolans has been illustrated in Fig 1. As observed in Fig 5, the strength of the control specimen (A) is equal to 15.6 MPa which is set as a criterion for further evaluations. According to Fig 5, at a replacement ratio of 7%, EP, IP, and RP enhance the strength by 18, 26 and 17%, respectively. As observed, the inclusion of 7% GP has reduced the compressive strength up to 5%

compared to the control specimen. However, as the GP content goes up, the strength improves by 15 and 36% following an increasing trend compared to the other specimens.

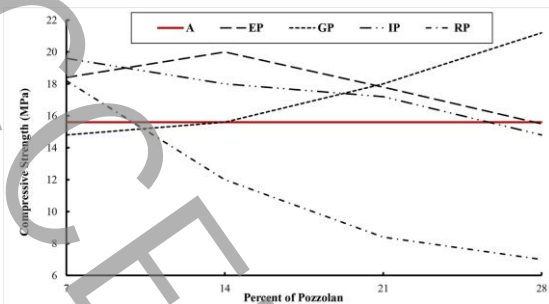


Fig 1. Compressive Strength Diagram

Tensile Strength Test

In general, except for RP by which the strength is improved only when the replacement ratio does not exceed 7%, the other pozzolans could desirably increase the strength up to the replacement ratio of 28%. Attention should be paid to the point that the size of particles greatly affects the results and thus, to preserve the margin of safety and decreasing trend of variations in tensile strength of some of the specimens, it is recommended to restrict the use of IP, EP, RP, and GP by the replacement ratio of 14%.

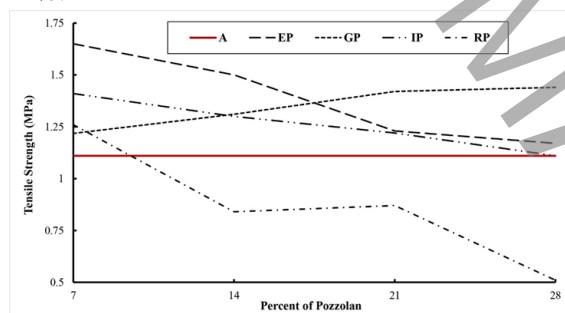


Fig 2. Tensile Strength Diagram

4. Conclusions

- It was observed that by replacing the cement with 7% eggshell, iron, and rubber powders, the compressive strength of the mortar improved by 18, 26 and 17%, respectively. However, the compressive strength declined by up to 5% in the specimens containing the GP which then, raised by 36% as the GP content increased. Generally, for the other specimens, an increase in the content of the powders has been followed by a decreasing trend in the compressive strength whose value remains greater than that of the control specimen yet. It was found that the maximum decline in the strength pertains to the cases containing the RP which

experienced up to 60% loss of strength that is most likely attributed to the insufficient adherence of the rubber, cement paste, and aggregates. As a general conclusion, the use of 14% pozzolanic wastes in the cementitious mortars desirably affects the compressive strength.

- The tensile strength could improve up to the replacement ratio of 28% except for the specimens containing the RP for which only 7% replacement is recommended. Quantitatively, the tensile strength of the control specimen and the specimens containing 28% glass, eggshell, and iron powders are equal to 1.11, 1.44, 1.17 and 1.11MPa, respectively. In general, the use of 7% of the powders, enhanced the tensile strength of all specimens.

- From the age of 7 to 28 days, the water absorption has significantly varied and on the contrary, at the ages of 28, 56 and 90 days, the water absorption has slightly changed. Accordingly, it was found that the EP and IP reduced the water absorption by 15 and 13% compared to the control specimen in which water absorption is about 19.5%. Moreover, it was observed that as per the increase in the GP content, water absorption decreases by 19%.

4. References

- [1] Mazzilli B, Palmiro V, Saueia C, Nisti MB. Radiochemical characterization of Brazilian phosphogypsum. *J Environ Radioact*2000;49:113–22.
- [2] Somlai J, Jobbagy V, Nemeth C, Gorjanacz Z, Kavasi N, Kovacs T. Radiation dose from coal slag used as building material in the Transdanubian region of Hungary. *RadiatProtDosimet*2006;118:82–7.
- [3] Binici H, Shah T, Aksogan O, Kaplan H. Durability of mortar made with granite and marble as recycle aggregates. *J Mater Process Technol*2008;208:299–308.
- [4] Binici H. Effect of crushed ceramic and basaltic pumice as fine aggregates on mortar properties. *Constr Build Mater* 2007;21:1191–7.
- [5] Karasahin M, Terzi S. Evaluation of marble waste dust in the mixture of asphaltic concrete. *Constr Build Mater* 2007;3:616–20.
- [6] Binici H, Kaplan H, Yılmaz S. Influence of marble and limestone dusts as additives on some mechanical properties of concrete. *Sci Res Essay* 2007;3:372–9.
- [7] Manaseer AA, Dalal TR. Concrete containing plastic aggregates. *ConcrInt*1997;19:47–52.
- [8] Soroushian P, Plasencia J, Ravanbakhsh S. Assessment of reinforcing effects of recycled plastic and paper in concrete. *ACI Mater J* 2003;100:203–7