

Evaluation of the effect of nano-CaCO₃ on the compressive strength of sandy clay soil with different percentage of clay

Mostafa Mohamamdi^a, Mahdi Khodaparast^{b*}, Ali M. Rajabi^c

^a Phd Candidate, Civil Engineering Department, University of Qom, Qom, Iran

mostafa4p@yahoo.com

^b Civil Engineering Department, University of Qom, Qom, Iran

khodaparast@qom.ac.ir

^c Engineering Geology Department, School of Geology, College of Science, University of Tehran, Tehran, Iran; amrajabi@ut.ac.ir

Abstract

Nanoparticles and Nano-reinforcement are extensively used in geotechnical engineering and there are various reports on the effect of nanomaterials on the improvement of the engineering properties of various soil types. The effect of nano calcium carbonate (nano CaCO₃) on the geotechnical properties of sandy clay (SC) soil containing different levels of clay was investigated. To this end, three types of SC soil containing 10, 20 and 30% clay and 0.3, 0.7, 1.1 and 1.5% nanoparticles were cured for 7, 14 and 28 days and then placed under uniaxial compression test. Also the experimental results were numerically analyzed by group method of data handling (GMDH) using artificial neural network. The samples were analyzed using XRD and SEM tests. According to the results, adding nano CaCO₃ to SC soils, caused an increase in the uniaxial compressive strength and secant modules. Moreover, the compressive strength obviously increased over time. An optimum nanoparticle level of 0.7% was obtained for the soils containing 20% and 10% clay. The corresponding nano CaCO₃ level for the soil containing 30% clay was 1.1%. The effect of nano CaCO₃ as an effective additive on the ultimate compressive strength of the soil was investigated by X-ray diffraction and SEM image and indicated an increase in the crystallinity of particles after adding CaCO₃ nanoparticles. Finally based on numerical analysis of experimental result, a correlation was obtained to predict the uniaxial compressive strength of the improved SC soil with a Mean error of 4%.

Keywords: Sandy clay, nano calcium carbonate, soil stabilization, uniaxial strength

* Corresponding Author: Email: khodaparast@qom.ac.ir

1. Introduction

In addition to traditional additives, the approach of using additives in nano-size has been recently considered. More atoms appear on the surface by decreasing particle size leading to the dominance of surface properties (such as physical, chemical, electrical and reactivity properties) and reduced importance of mass properties. Larger surface-to-volume ratios (i.e. specific surface area) are obtained in nanoscale leading to a higher cation exchange capacity. Example of studies on the application of nanomaterials in geotechnical engineering, especially in the improvement of problematic soils, are reviewed below. Gallagehr and Finstere (2004); Burton et al. (2009) and Changizi and Haddad (2015) studied the effect of silica nanoparticles on clay soil properties and reported that addition of small amounts of nano-silica increased the cohesion of clay [1,2,3,]. Yao et al. (2019) studied the effect of magnesium oxide nanoparticles on cement-stabilized soft soil. They found the significant role of MgO nanoparticles on the strength properties of cement-stabilized soft clay [4]. According to nano-geotechnical engineering literature, experimental studies have focused on some nanomaterials (including nanosilica, nanoclay, and nano iron oxide) but few studies were found on nano calcium carbonate (CaCO_3) as a secondary stabilizer from a geotechnical point of view. Due to widespread geological dispersion of calcium carbonate and application of calcium carbonate in soil improvement methods such as injection and deep mixing, it is necessary to investigate the effect of nano CaCO_3 on soil properties. Accordingly, this experimental study investigated the effect of CaCO_3 nanoparticles on sandy clay soils. Also, using artificial neural network method with GMDH method, a correlation is presented for predicting uniaxial strength of SC soils stabilized with nano CaCO_3 .

2. Methodology

The effect of nano CaCO_3 on uniaxial compressive strength of sandy clay soil was studied experimentally. To this end, sandy clay was prepared from the Caspian Sea coast in northern Iran and clay soil (kaolinite) was purchased from Iran China Clay Industries. The sandy soils used in this study was SP class with the average particle size (D_{50}) of sandy soil equals 0.21 mm. the clay soil used in this study is placed in the CL class and According to the results of chemical analysis, the main elements in the soil include Si, O, and Al. To study the effect of calcium carbonate nanoparticles on sandy clay soil, SC1, SC2 and SC3 soils respectively with 10, 20 and 30% clay were used. The physical characteristics of

these three soil types are summarized in Table 1. According to previous studies and considering that the Nano CaCO_3 used in this study will probably react with the clay part of the soil, different percentages of clay were used to investigate the reactivity of this soil and Nano CaCO_3 .

Table 1. Physical properties of soils used in this study.

Soil properties	Description	SC1	SC2	SC3
FC(%)	Fine Percent	10	20	30
$G_s(\text{kg/m}^3)\times 10^3$	Specific Gravity	2.66	2.64	2.62
$\gamma_d(\text{kg/m}^3)\times 10^3$	Maximum Dry Density	2.04	2.01	1.99
LL(%)	Liquid Limit	18	19	22
PL(%)	Plastic Limit	14	14	16
PI(%)	Plasticity Index	4	5	6
OWC(%)	Optimum water content	12	14	17

For samples preparation (specimens SC1, SC2, and SC3 in Table 2), after preparing a homogenous mixture of the soils with certain levels of nano CaCO_3 (0.3, 0.7, 1.1 and 1.5%), the mixture was compacted in five layers in a cylindrical mold. A total of 72 specimens were prepared to evaluate the effect of nano CaCO_3 on the strength properties of the soil. Then, uniaxial compressive strength test was performed on these samples and samples without additives in three processing times of 7, 14 and 28 days according to ASTM C617 standard. Also Using the results of experiments on sandy clay (SC) soil specimens, a correlation was proposed for predicting the uniaxial strength of soils based on GMDH method. The data used in this study include nanoparticle level (N), sand level (S), clay level (C) and curing duration (t). These data are used as inputs to the neural network model. The objective function of the neural network model is uniaxial compressive strength of the soil which is determined experimentally. Using experimental results and taking into account research variables, a correlation is presented for predicting the uniaxial compressive strength of SC soils stabilized with nano CaCO_3 .

3. Discussion and Results

To evaluate the effect of nano CaCO_3 on the strength of fine-grained cohesive SC soils, the results of the uniaxial compressive strength tests are analyzed. For

example, Figure 1 shows the Ultimate Strength of Stabilized Soils with Different Nanoparticle Contents at Curing Time of 28 days.

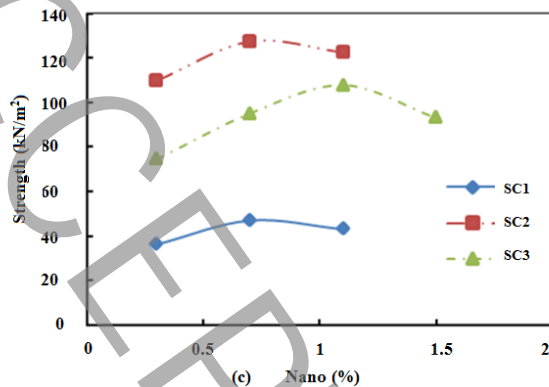


Figure1: Ultimate Strength of Stabilized Soils with Different Nanoparticle Contents at Curing Times of 28 days

According to the results, unlike SC1 and SC2 stabilized, the strength of SC3 increases as nanoparticle level increases from 0.7 to 1.1%. Scrutiny on stress-strain diagrams for all three specimens show that the uniaxial compressive strength increases at all curing durations indicating the occurrence of chemical reactions between soils and nano CaCO₃. The strain also increases with increasing clay level. Moreover, the stress-strain behavior of soil specimens becomes more linear with increasing nano CaCO₃ level leading to an increase in the modulus of elasticity. Also X-ray diffraction (XRD) analysis was used to determine phase structure and degree of crystallinity of the soil specimens' stabilized and non-stabilized with nano CaCO₃. The result showed the products of calcium silicate hydrate (CSH) reaction and quartz and kaolin byproducts. The intensity of peaks indicates the high degree of crystallinity of the specimens containing nanoparticles. In numerical part of study 33 experimental data were used to predict the uniaxial compressive strength of the soil by GMDH method. The input data were divided into training and test data. Of 33 experimental data obtained in the previous stage, 26 specimens were used for designing GMDH structure and the remaining 7 specimens were used for evaluating the performance of the network in predicting uniaxial compressive strength. The GMDH method with 2 hidden layer was considered to obtain a polynomial for predicting the uniaxial compressive strength of the soil where N, S, C, and t respectively represent nanoparticle level, sand level, clay level and curing duration.

In order to evaluate the presented artificial neural network, the statistical index of relative error percentage has been used and considering that the relative error rate obtained from GMDH algorithm is 4.5%, the results

indicate the high efficiency and accuracy of this method.

4. Conclusion

In this paper, the effect of nano CaCO₃ on the strength properties of three soils with different sand and clay levels was evaluated by uniaxial compressive test. According to the results, adding nano CaCO₃ to all specimens caused an increase in the ultimate strength of soil specimens. An optimal additive level of 0.7% for SC1 and SC2 and 0.9% for SC3 was obtained. The ultimate strength of all specimens increased with increasing age. The specimen SC1 showed the lowest strain at failure (brittle behavior) due to its granular nature. The strain at failure decreased by adding nano CaCO₃ to the soil. The strain at failure of specimens increased with increasing the clay level. The soil specimen SC2 showed higher strength than the other two specimens given the clay level in the sandy soil. This can be related to the clay level and maximum filling of voids between sand grains. In other words, clay soil has the highest contribution in filling voids between sand grains without displacing grains and with the lowest negative impact on intra-grain friction of the soil. The microstructure analysis by X-ray diffraction shows high degree of crystallization and formation of CSH crystalline phase at 25.3° and 26.9°. Experimental results were numerically analyzed by GMDH method to predict uniaxial compressive strength. The results indicated a Mean error of 4.5% representing high consistency of estimation function and experimental results.

5. References

- [1] Gallagher, P. M., and Finstere, S. (2004). " Physical and numerical model of colloidal silica injection for passive site stabilization. " *Vadose Zone Journal.*, (3),917-925.
- [2] Butron, C., Axelsson, M., and Gustafson, G. (2009). " Silica sol for rock grouting: Laboratory testing of strength fracture behavior and hydraulic conductivity. " *Tunneling and underground space technology.*, (24), 603-607.
- [3] Changizi, F., and Haddad, A. (2015). " Strength properties of soft clay treated with mixture of nano-SiO₂ and recycled polyester fiber. " *Journal of rock mechanics and geotechnical engineering.*, (29), 367-378.
- [4] Yao, K., Wang, W., Li, N., Zhang, C., and Wang, L. (2019). " Investigation on strength and Microstructure characteristics of Nano-Mgo admixed with cemented soft soil. " *Construction and Building Materials.*, (206), 160-168.