

The Effect of Emboss Fiber (Modified Polypropylene Fiber) on the Behavior of Concrete used in Concrete Pavements

Masood Gholami¹, Fereidoon Moghadas nejad^{2*}, Ali Akbar Ramezani pour³, Amir Mohammad Ramezani pour⁴

¹ PhD student, Department of Civil & Environmental Engineering, Amirkabir University of Technology, Tehran, Iran

² Professor, Department of Civil & Environmental Engineering, Amirkabir University of Technology, Tehran, Iran

³ Professor, Department of Civil & Environmental Engineering, Amirkabir University of Technology, Tehran, Iran

⁴ Associate Professor, Department of Civil Engineering, University of Tehran, Tehran, Iran

ABSTRACT

Concrete pavements are widely used by pavement engineers due to their advantages over flexible pavements such as longer lifetime, good performance and durability, etc. However, concrete pavements represent some drawbacks such as shrinkage that increases the tensile stress in concrete, which may lead to cracking, warping, etc. Drying shrinkage is the most important type of shrinkage in concrete pavements. polypropylene fibers can be used to control or reduce width of cracking by bridging both sides of crack. In this study, the effect of Emboss fiber on the behavior of concrete pavement was investigated. Slump, compressive strength, third-point flexural strength, electrical resistance, skid resistance, free shrinkage and restrained shrinkage by ring test were performed. Two water-cement ratios of 0.35 & 0.4 were used for mix design and the percentage of polypropylene fiber used in mixtures was 0.44% by concrete volume. The results showed that the use of Emboss Fiber reduced the workability of concrete. Also, these reinforcements had different effects on compressive and flexural strength and electrical resistance depend on homogeneity of Emboss fiber reinforced concrete. Furthermore, toughness indices and energy absorption of concrete were significantly increased by using Emboss fiber reinforced concrete. In addition, using fiber indicated a slight reduction in the amount of free and restrained shrinkage and occurrence of first-crack. Polypropylene fibers had a key role in controlling crack width by bridging both sides of crack. Finally, no certain relationship was observed between using SRA and changing the skid resistance of concrete pavement

KEYWORDS

Concrete pavement, Drying shrinkage, Shrinkage cracks, Emboss Fibers, polypropylene Fibers

* Corresponding Author: Email: moghadas@aut.ac.ir

Introduction

Concrete pavements are widely used due to their pros over flexible pavements such as longer lifetime, good performance and durability, etc. [1]. However, there are some drawbacks like drying shrinkage that define as the contracting of a hardened concrete mixture due to the loss of capillary water [2]. Also, shrinkage may lead concrete pavement to cracking, warping & curling and cause a reduction on performance and lifetime [3, 4].

Fibers are one of the materials that use for controlling shrinkage cracks width by bridging between both sides of crack walls [5, 6].

The effect of using polypropylene fiber on behavior of concrete was investigated by Ramezaniapour et al. [5]. The results showed that using fiber led to reduce the value of compressive, flexural & tensile strength of concrete because of increasing porosity of concrete. Mo et al. [7] remarked that using polypropylene fiber had contradictory effect on compressive strength but improved ductility of concrete. Also, Wang et al. [8] investigated the effect of polypropylene fibers on the behavior of high-performance concrete and reported that using fibers improve the mechanical properties of concrete. Gong et al. [9] represented that drying & autogenous shrinkage of concrete decrease by using polypropylene fiber as a reinforcement. Badogiannis et al. [10] reported that using fiber reduce and delay concrete shrinkage.

Controlling the shrinkage phenomenon on concrete pavement have some advantages such as increasing concrete slabs length and rate of implementation. Different effect of fibers on mechanical and durability properties of concrete, was an important challenge to use this material as a reinforcement. In this study, the effect of Emboss fiber on the behavior of concrete used in concrete pavements was investigated

Materials and Methods

Type II Portland cement produced by Tehran cement factory was used in this study with density of 3130 kg/m³.

Furthermore, 3 types of aggregates were used in this study: gravel 9.5-19 mm, gravel 6-12 mm and sand 0-6 mm. the proportion of each types of aggregates were 20%, 25% and 55% of total weight, respectively. Also, the properties of Emboss Fiber and superplasticizer are shown in table 1:

Table 1: Properties of Emboss fiber & Superplasticizer

name	density (gr/cm ³)	nature
Emboss Fiber	0.91	Polypropylene
superplasticizer	1.05	Polycarboxylate, non-ionic

The mix composition was obtained based on national method for concrete mix design [11] with two W/C of 0.35 & 0.4 and the amount of cement was 400kg/m³. In addition, the percentage of Emboss fiber was 0.44 by volume of concrete. Table 2 displays four concrete mix composition investigated in this study:

Table 2: Concrete mix Composition (per cubic meter)

Name	OPC 0.35	Fiber 0.35	OPC 0.4	Fiber 0.4
W/C	0.35	0.35	0.4	0.4
Cement (kg)	400	400	400	400
Gravel 9.5-19 (kg)	375.6	375.6	365.3	365.3
Gravel 6-12 (kg)	469.5	469.5	456.6	456.6
Sand 0-6 (kg)	1032.8	1032.8	1004.6	1004.6
Water (kg)	140	140	160	160
Superplasticizer (kg)	2	3	1.6	1.6
Emboss Fiber (kg)	0	4	0	4
Density (kg/m ³)	2372	2363	2344	2334
Slump (mm)	63	68	60	52

Also, Slump, compressive strength, flexural strength with center point loading, electrical resistance, skid resistance, free shrinkage and restrained shrinkage were performed as experimental program.

Results and discussion

Results of Slump flow for each mix compositions were represented in table 2. It shows that decreasing W/C or using Emboss Fiber effectively reduced workability of concrete.

Results of compressive and flexural strengths were shown in figure 1. As it can be seen, W/C has a reverse effect on mechanical properties of concrete. It might be due to reduction of matrix and non-react water and increase aggregate after decreasing water-cement ratio.

Using Emboss fiber had different effect on mechanical properties of concrete in different W/C, because using fiber increases concrete heterogeneity that effect on mechanical properties [5]. Furthermore, using Emboss fiber increased amount of dissipated energy and ductility of concrete.

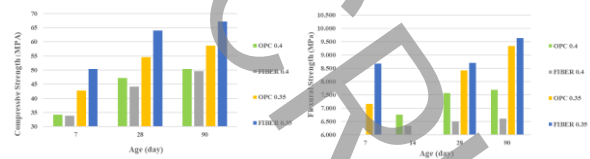


Figure 1: Compressive (left) and Flexural (Right) Strength results

Figure 2 represented the results of electrical and skid resistance. It was observed that electrical resistance and mechanical properties had similar behavior in fiber

reinforced concrete mixes. Also, there is no certain relationship between skid resistance results and types of concrete at constant W/C. In addition, electrical & skid resistance of concrete improved at lower W/C.

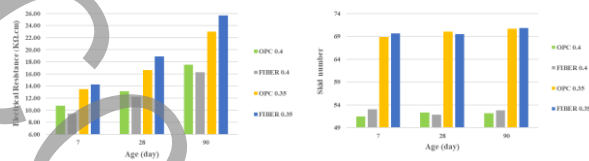


Figure 2: electrical (left) and skid (Right) resistance results

Figure 3 showed the effect of Emboss fiber on the behavior of free and restrained shrinkage (restrained shrinkage was tested on concrete with W/C=0.35). Using fiber improved concrete mixtures against free shrinkage (length change) and the ring's strain of restrained shrinkage. The reason is that cement paste was absorbed by fibers. Also, aggregates can better interlock together after using fiber in concrete mixtures [6, 12]. Furthermore, Emboss fiber decreased the crack width and number of cracks. It might be happened because fiber try to control the width of crack by bridging between both sides of crack walls [13].

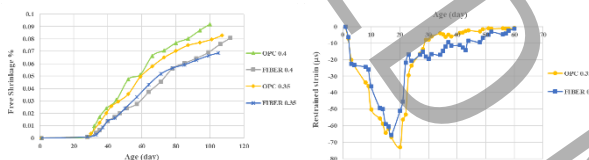


Figure 3: Free (left) and restrained (Right) shrinkage

Conclusion

This research tried to investigate the effect of Emboss fiber on the mechanical and durability properties of concrete used in concrete pavements. The results of this study can be summarized as follows:

- The use of Emboss fiber cause a reduction on slump flow & workability of concrete because of preventing aggregates and cement paste to move freely.
- This material had different effect on compressive and flexural strengths of concrete at each W/C. It happens because using fiber increases concrete heterogeneity that should be controlled. Furthermore, using Emboss fiber increased the ductility of concrete.
- Electrical resistance of concrete represented different behavior after using fiber at two mixtures with different W/C. It might be caused by increasing heterogeneity of concrete.
- There was no certain effect between using Emboss fiber and variation of skid resistance.
- Free and restrained shrinkage had been reduced about 10 & 20 percent by using fiber, respectively. In addition, the crack width decreased about 35% which shows using fiber had a desirable effect on controlling shrinkage and

its cracks. Fiber can act as a bridge between both sides of crack walls and prevent the growth of crack.

References

- [1] R.A. Embacher, M.B. Snyder, Life-cycle cost comparison of asphalt and concrete pavements on low-volume roads; case study comparisons, Transportation research record, 1749(1) (2001) 28-37.
- [2] D. Mostofinejad, Reinforced Concrete Structure, Arkan-e danesh publication, Volume 1 (2017).
- [3] J.M. Ruiz, R.O. Rasmussen, G.K. Chang, J.C. Dick, P.K. Nelson, Computer-based guidelines for concrete pavements, volume II: design and construction guidelines and HIPERPAVE II user's manual, Federal Highway Administration, FHWA-HRT-04-122 (2005).
- [4] J.-H. Nam, S.-M. Kim, M.C. Won, Measurement and analysis of early-age concrete strains and stresses: continuously reinforced concrete pavement under environmental loading, Transportation research record, 1947(1) (2006) 79-90.
- [5] A. Ramezani pour, M. Esmaili, S. Ghahari, M. Najafi, Laboratory study on the effect of polypropylene fiber on durability, and physical and mechanical characteristic of concrete for application in sleepers, Construction and Building Materials, 44 (2013) 411-418.
- [6] M. Hsie, C. Tu, P. Song, Mechanical properties of polypropylene hybrid fiber-reinforced concrete, Materials Science and Engineering: A, 494(1-2) (2008) 153-157.
- [7] J. Mo, L. Zeng, Y. Liu, L. Ma, C. Liu, S. Xiang, G. Cheng, Mechanical properties and damping capacity of polypropylene fiber reinforced concrete modified by rubber powder, Construction And Building Materials, 242 (2020) 118111.
- [8] D. Wang, Y. Ju, H. Shen, L. Xu, Mechanical properties of high performance concrete reinforced with basalt fiber and polypropylene fiber, Construction and Building Materials, 197 (2019) 464-473.
- [9] J. Gong, W. Zeng, W. Zhang, Influence of shrinkage-reducing agent and polypropylene fiber on shrinkage of ceramsite concrete, Construction and Building Materials, 159 (2018) 155-163.
- [10] E. Badogiannis, K. Christidis, G. Tzanetos, Evaluation of the mechanical behavior of pumice lightweight concrete reinforced with steel and polypropylene fibers, Construction and Building Materials, 196 (2019) 443-456.
- [11] Building and housing research center, The national Method for concrete mix design, BHRC Publication, No. S-479 (2008).
- [12] R. Olaoye, J. Oluremi, S. Ajamu, The use of fibre waste as complement in concrete for a sustainable environment, Innovative Systems Design and Engineering, 4(9) (2013) 91-97.
- [13] A. Caggiano, S. Gambarelli, E. Martinelli, N. Nisticò, M. Pepe, Experimental characterization of the post-cracking response in hybrid steel/polypropylene fiber-reinforced concrete, Construction and Building Materials, 125 (2016) 1035-1043.