



Investigation of the Effect of Polypropylene Fibers on Compression Strength and Tensile Strength of Organic Soil Stabilized with Lime and Xanthan-Gum Bio-Polymer

B. Ebrahimi Alavijeh, B. Zare, M. Mokhtari*

Civil Engineering Department, Yazd University, Yazd, Iran.

ABSTRACT: The presence of organic matter in soil reduces its compressive and shear strength. It is, therefore, not suitable for construction projects. Soil strength can be enhanced by various methods. Stabilization and reinforcement are two common ways of improving soil strength parameters. In this study, the effect of polypropylene fibers on stabilized soil was investigated. For this purpose, lime and xanthan gum biopolymer were used as stabilizers, and soil was reinforced with polypropylene fibers. The experiments were performed using 1 and 3% lime, 1 and 1.5% xanthan gum biopolymer, and 0.5% polypropylene fibers (by dry weight). To investigate the effect of these materials on soil strength, uniaxial compression strength and indirect tensile strength tests were conducted. The processing time of the samples was 7 and 21 days. The results showed that the addition of lime, xanthan gum biopolymer, and polypropylene fibers can increase the compression strength of the soil. Increasing the processing time can also increase the strength of stabilized soil, and the addition of fibers leads to the improvement of soil ductility. The maximum tensile strength was observed in the sample stabilized with xanthan gum biopolymer. In the soil sample with 1% lime, the addition of fibers could increase the soil tensile strength. The results suggest that soil strength parameters can considerably be improved if xanthan gum is replaced with lime. In addition, this material is environment-friendly.

Review History:

Received: Oct. 11, 2019
Revised: Dec. 28, 2019
Accepted: Jan. 08, 2020
Available Online: Mar. 01, 2020

Keywords:

Organic Soil
Lime
Xanthan Gum Biopolymer
Polypropylene Fibers
Compression And Tensile Strength

1- Introduction

Soils containing a high percentage of organic matter are not suitable for road construction projects. This is due to the low shear strength and high compressibility of those types of soil. An increased percentage of organic matter can decrease soil resistance and pH [1]. One of the previous methods of constructing roads on organic soil beds was soil replacement or preloading to improve soil engineering parameters [2]. The chemical stabilization of soil using traditional materials such as lime, cement, and fly ash [2] or new materials such as polymers and biopolymers is another option to improve the resistance parameters of different soil types [3]. Increasing the bearing capacity of soil makes it possible to use it in road construction projects. Xanthan gum biopolymer increases soil compressive strength, and an increase in the curing time / raises its resistance [4, 5].

Synthetic fibers include polypropylene, polyester, polyethylene, glass, and polyvinyl alcohol fibers [6]. The addition of these materials to soil can generally increase its compressive and shear strengths [6, 7].

In this study, lime stabilizers, xanthan gum biopolymer, and yarn waste fibers have been used as reinforcing materials of polypropylene to improve the resistance parameters of organic soil. The evaluation of compressive and tensile

strengths was conducted for organic soil samples: a) stabilized with lime and xanthan gum, b) simultaneously stabilized and reinforced with lime + fibers and xanthan gum, and c) stabilized and reinforced with lime + fibers and xanthan gum + fibers. Then, the samples were compared after 7 and 21 days of curing.

2- Methodology

The soil used in this study was an organic type of soil containing 67-69.1% organic matter. Lime, xanthan gum biopolymer, and polypropylene BCF waste fibers were used to optimize the soil features. In terms of dry weights, 1% and 3% w/w of lime, 1.5% w/w of biopolymer, and 0.5% w/w of fibers served the purpose. Tables 1 to 3 indicate the features of soil, xanthan gum, and fibers, respectively.

3- Results and Discussion

The addition of lime, xanthan gum, and fibers to organic soil increased its compressive and tensile strengths. The addition of fibers to the soil stabilized with lime and xanthan gum increased the soil flexibility. Figs. 1 and 2 indicate the effect of adding fibers on the compressive strength of the soil stabilized with lime and xanthan gum in a 7-day curing time, respectively.

*Corresponding author's email: mokhtari@yazd.ac.ir



Table 1. Features of the organic soil used in the study

Feature	Value
Natural moisture percentage	262-328
The ratio of the initial pores	5.8
Specific density	2.11
Percentage of organic matter	67-69.2
Ash rate	21-25
pH	6.5
Maximum dry density (gr/cm ³)	1.13
Percentage of optimum moisture	38.89

Table 2. Technical properties of xanthan gum

Feature	Unit
Physical features	White or light yellow powder
Sieved 200 (%)	More than 92
Sieved 100 (%)	100
Viscosity	1200-1700
Weigh loss due to drying (%)	Less than 15
pH	6-8
Ash (%)	Less than 16

Table 3. Properties of BCF fibers

Property	Value	Unit
Density	0.91	(gr/cm ³)
Diameter	45	μm
Length	1-2	cm
Tensile strength	100	MPa

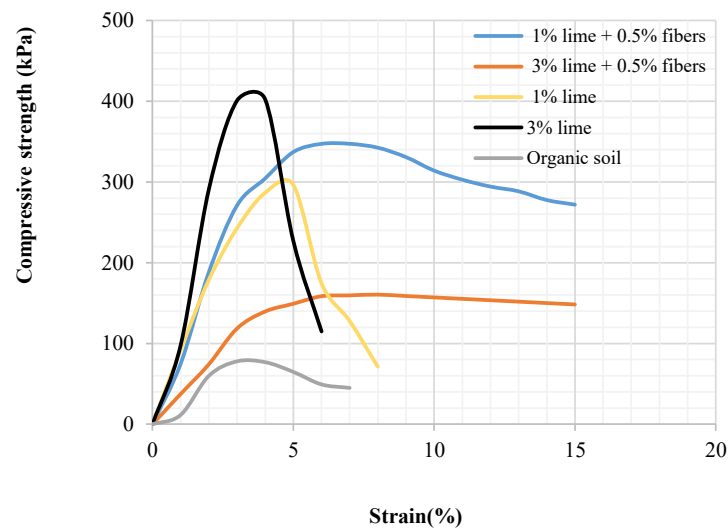


Fig. 1. The effect of BCF waste polypropylene fibers on the compressive strength of the soil stabilized with lime in a 7-day curing time (the optimum moisture from the compaction test)

Increasing the curing time led to an increase in the compressive strength of the specimens, the results of which are indicated in Table 4. Table 5 indicates the tensile strengths of the specimens after 7 and 21 days of curing. Increasing the curing time also enhanced the tensile strength. The addition of

fibers to the soil stabilized with 1% lime improved its tensile strength. The findings of this study on the enhancement of the compressive strength of the soil stabilized with lime and xanthan gum are in line with the results of previous research [4, 5, 8, 9].

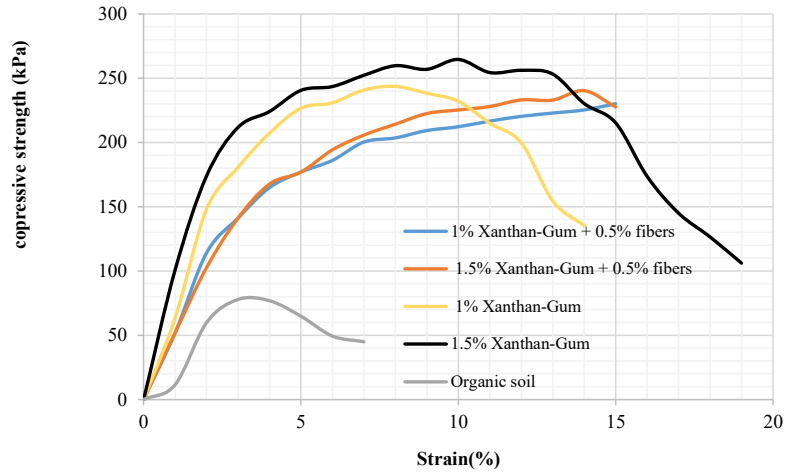


Fig. 2. The effect of BCF waste polypropylene fibers on the compressive strength of the soil stabilized with xanthan gum in a 7-day curing time (the optimum moisture from the compaction test)

Table 4. The effect of increased curing time on compressive strength

Percentage of materials added	7-day compressive strength	21-day compressive strength
1% lime	296.7284	420.2116
3% lime	402.2857	430.2222
1% xanthan gum	243.6296	322.1429
1.5% xanthan gum	264.5238	426.9048
1% lime + 0.5% fiber	347.46	487.0935
3% lime + 0.5% fiber	160.6186	246.0395
1% xanthan gum + 0.5% fiber	230.0164	535.5119
1.5% xanthan gum + 0.5% fiber	240.2296	333.8947

Table 5. The effect of increased curing time along with the addition of fibers on tensile strength

Percentage of materials added	7-day tensile strength	21-day tensile strength
1% lime	46.07117	56.20682
3% lime	49	59
1% xanthan gum	60.81394	78.7817
1.5% xanthan gum	66.80319	85.69237
1% lime + 0.5% fiber	58.04967	82.9281
3% lime + 0.5% fiber	24.87843	38.69978
1% xanthan gum + 0.5% fiber	41.46405	58.04967
1.5% xanthan gum + 0.5% fiber	49.75686	58.04967

4- Conclusion

Stabilization and reinforcement are two common methods to improve soil engineering parameters in civil projects. The potential improvement of tensile and compressive strengths of organic soil was examined in the present study. Accordingly, lime and xanthan gum were used as stabilizers while polypropylene fibers were employed as

reinforcing elements. The results indicated that lime, waste fibers of polypropylene yarn, and xanthan gum biopolymer can each increase the compressive strength of soil alone. In soil stabilized with fibers, the application of a vertical force among soil particles can lead to cohesion, and the sum of this cohesion and friction among the soil particles reinforces the tensile stress in the fibers and increases the compressive

strength. An increase in the lime percentage can enhance soil resistance due to improved soil particle reactivity as a result of the increase in soil calcium and hydroxide. The reactions between calcium ions and soil particles increase the strength and the cementation of organic soil stabilized with lime. The addition of xanthan gum to soil also increased the adhesion of its particles, thereby increasing its strength.

References

- [1] Kim, Y.-T., and Pradhan, B., 2016. "Mechanical and germination characteristics of stabilized organic soils". *Marine Georesources & Geotechnology*, 34(7), pp. 681-688.
- [2] Tastan, E.O., Edil, T.B., Benson, C.H., and Aydilek, A.H., 2011. "Stabilization of organic soils with fly ash". *Journal of geotechnical and Geoenvironmental Engineering*, 137(9), pp.819-833.
- [3] Zandieh, A.R., and Yasrobi, S.S., 2010. "Retracted article: Study of factors affecting the compressive strength of sandy soil stabilized with polymer". *Geotechnical and Geological Engineering*, 28(2), pp.139-145.
- [4] Chang, I., Im, J., Prasadhi, A.K., and Cho, G.-C., 2015. "Effects of Xanthan gum biopolymer on soil strengthening". *Construction and Building Materials*, 74, pp.65-72.
- [5] Latifi, N., Horpibulsuk, S., Meehan, C.L., Majid, M.Z.A., and Rashid, A.S.A., 2016. "Xanthan gum biopolymer: an eco-friendly additive for stabilization of tropical organic peat". *Environmental Earth Sciences*, 75(9), pp.825.
- [6] Islam, S., Hoque, N.R., Haque, M.A., Mishra, P.N., Mamun, M. and Dey, S., 2019. "Strength development in fine-grained paddy field soil by lime addition". *Journal of Building Engineering*, 26, pp. 100857.
- [7] Hejazi, S.M., Sheikhzadeh, M., Abtahi, S.M. and Zadhoush, A., 2012. "A simple review of soil reinforcement by using natural and synthetic fibers". *Construction and Building Materials*, 30 (2012) 100-116.
- [8] Priya, C.S., Archana, S., Albert, A.B., and Deeraj, A., 2017. "Stabilization of clayey soil using polypropylene fiber". *International Research Journal of Engineering and Technology (IRJET)*, 4(4), pp.1252-1255.
- [9] Latifi, N., Horpibulsuk, S., Meehan, C.L., AbdMajid, M.Z., Tahir, M.M., and Mohamad, E.T., 2016. "Improvement of problematic soils with biopolymer—an environmentally friendly soil stabilizer". *Journal of Materials in Civil Engineering*, 29(2).

HOW TO CITE THIS ARTICLE

B. Ebrahimi Alavijeh, B. Zare, M. Mokhtari., *Investigation of the Effect of Polypropylene Fibers on Compression Strength and Tensile Strength of Organic Soil Stabilized with Lime and Xanthan-Gum Bio-Polymer. Amirkabir J. Civil Eng.*, 53 (5) (2021) 423-426

DOI: [10.22060/ceej.2020.17185.6490](https://doi.org/10.22060/ceej.2020.17185.6490)

